

# Design and Development of Instant Linear Gel for Coal Bed Methane Gas Operations

R. V. V. Ramana Murthy<sup>a</sup>, K.S.R. Murthy<sup>b</sup>, Murthy Chavali<sup>c,d</sup>

<sup>a</sup>Division of Chemistry, Department of Sciences and Humanities, Vignan's Foundation for Science, Technology and Research University (Vignan's University), Vadlamudi 522 213 Guntur District, Andhra Pradesh, India

<sup>b</sup>Department of Applied Chemistry, University of Petroleum and Energy Studies, Energy Acres, Bidholi Campus, Premnagar, Dehradun, Uttarakhand 248007, India

<sup>c</sup>PG Department of Chemistry, Dharma Appa Rao College (DARC), Nuzvid 521 201 Krishna District, Andhra Pradesh, India

<sup>d</sup>NTRC-MCETRC and Aarshanano Composite Technologies Pvt. Ltd., Guntur District, Andhra Pradesh, India

## Abstract

Linear gel fracturing fluids are expressed with an extensive range of materials/polymers in an aqueous base. Earlier we developed fracturing linear gel with fossil diesel, bio-diesel and also used suspending anti-settling agents and emulsifiers. Here we report on a novel and an efficient method for the preparation of linear gel direct mix with water, guar gum and sodium acetate together instantly. In this research work, we used water instead of diesel without any need to mix anti-settling agents, suspending agents, emulsifiers that resulted in 30 viscosity linear gel. Degradation pattern observed from the breaker test showed that a reduction in gel viscosity depends on time, temperature & breaker concentration. Ammonium persulphate or Ammonium per oxidisulphate and enzyme-G were used for oxidation purpose to break the gel gradually at a particular static temperature. Observations from experiments revealed that a small concentration of breaker provides rapid break compared to oxidative breakers. This article, designing of fracturing fluids describes how to use the fluid's viscosity generated by the gelling agents like guar gum for CBM operations.

© 2021 Author(s).

**Keywords:** Breakers; CBM operation; fragmentation; linear gel; viscosity properties.

## 1. Introduction

Hydraulic fracturing typically involves millions of gallons of fluid that are pumped into oil or gas well at high pressure to create fractures in the rock formation that allow oil or gas to flow from the fractures to the wellbore [1]. The main functions of fracturing fluids are to open the fracture and to transport propping agents along the length of the fracture. They are four types of fracturing i.e. water fracturing, gelled fluids, linear gels, crosslink gels [2]. The chemistry of commonly used fracturing fluids and additives are guar [Fig. 1]. Guar has a long polymer chain and high

\* Corresponding author.

E-mail address: [chavalim@outlook.com](mailto:chavalim@outlook.com) (Murthy Chavali)

molecular weight [Fig. 2]. Gymer composed of Mannose and galactose sugars has a high affinity for water. When the powder added to water, the guar particles swell and hydrate, which means the polymer molecules become associated with many water molecules and unfold and extend out into the solution which tends to overlap and hinder motion, which elevates the viscosity of the solution [3].

The guar polymer has chemicals added to the fracturing fluids include friction reducers, surfactants, gelling agents (guar gum), scale inhibitors, acids, corrosion inhibitors, antibacterial agents. Depending on the site, 15-80 % of the fracturing fluid injected is recovered as flow backwater at the wellhead [16]. Biocides/Bactericides are added to minimize the enzymatic attack of the polymers used to gel the fracturing fluid by aerobic bacteria present in the base water [4]. Agro material while preparation of frac concentration should be in basic nature. So we can use Sodium bicarbonate or sodium acetate is mixed in the concentration to maintain the pH [17].

Usually, the gelling agents in fracturing fluids are guar gum derivatives such as hydroxyl propyl guar and carboxymethyl hydroxyl propyl guar (or) cellulose derivatives such as carboxyl methyl guar, hydroxyl ethyl cellulose, hydroxypropyl cellulose, xanthan gum [5]. Before starting frac operation need to add biocide (anti-bacterial agent) in water tanks, it will control the growth of micro-organisms will quickly degrade the polymer to a non-functional level [18]. So the addition of biocides and bactericides to fracturing fluids will prevent the introduction of anaerobic sulphate reducing bacteria (SRB) into the reservoir [6].

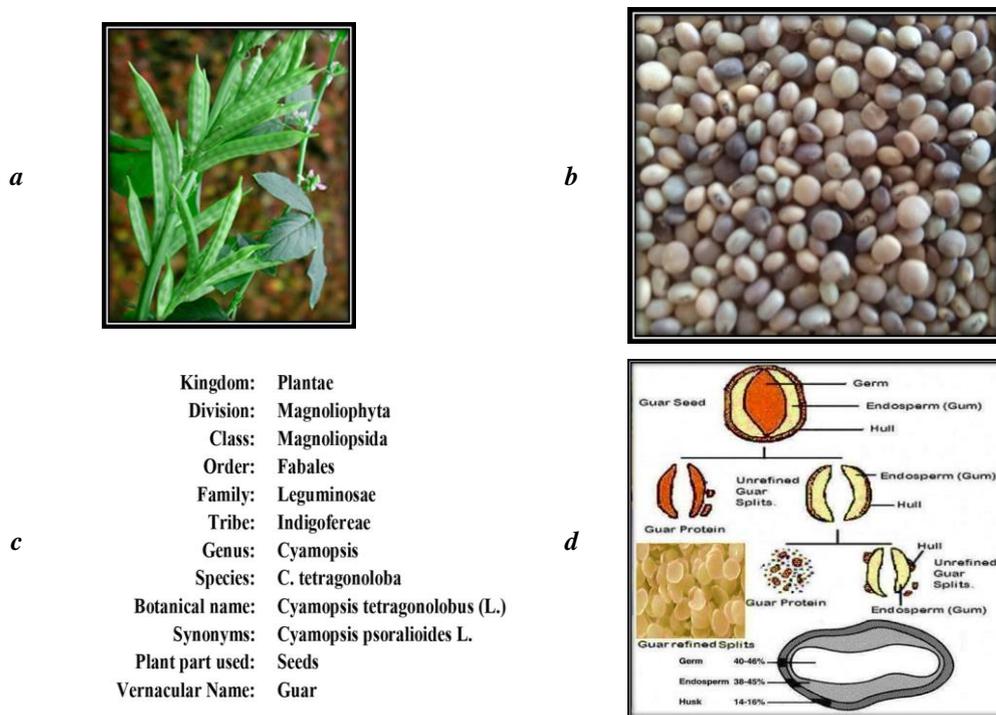


Fig.1 a. Guar gum plant b. Guar seeds c. Guar scientific classification d. Seed anatomy

Guar galactomannan is a plant polysaccharide with extensive applications in food, paper, and textile and petroleum industries [7]. The main advantages of using guar are its low cost, easy availability and capacity to form viscous solutions and gels at low concentration. Additionally, chain architecture of guar galactomannan can be selectively modified to tailor properties of guar formulations and open up new opportunities for guar usage [8].

In many types of shale, proppant conductivity drops considerably in the presence of water because the rock-fluid interactions soften the rock leading to proppant embedment [9]. The fracturing treatments require a higher viscosity fluid, such as linear fracturing fluids [10]. These are formulated by adding a wide array of different polymers to water [11]. Such polymers are dry powders that swell when mixed with an aqueous solution and form a viscous gel [12].

Linear gels control fluid loss very well, whereas in higher permeability formations fluid loss can be excessive [19, 20]. Linear gels tend to form thick filter cakes on the face of lower-permeability formations [14].

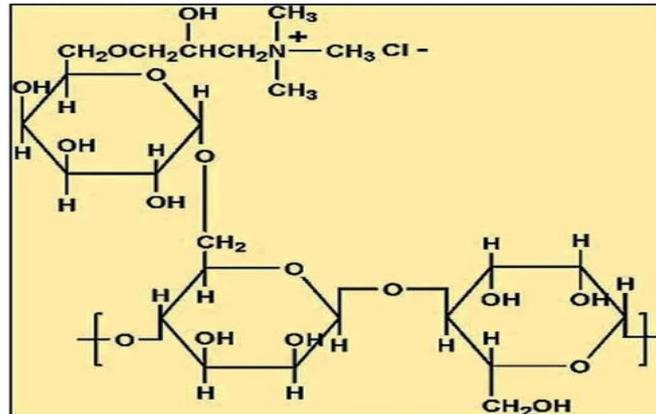


Fig. 2 Chemical structure of guar gum

So this study provides focuses the way to mix the fracturing fluid, how Linear gel hydrating and how to perform breaker test [15]. The guar gum has many derivatives like mannose and galactose. Now a day, more derivatives are looking very fine gives good viscosity properties. Guar gum powder is hydrated with water then the molecules unfold tends to which elevator the viscosity of the solution [21].

In general, a fracturing fluid can be thought of as the sum of three main components:

$$\text{Fracturing Fluid} = \text{Base Fluid} + \text{Additives} + \text{Proppant}$$

## 2. Materials and methods

### 2.1. Experimental

1. Production water
2. Sodium bicarbonate or sodium acetate as a buffering agent.
3. Guar gum powder [Fig. 3].
4. Two breakers, Ammonium per Sulphate which is in solid-state and another one is liquid Hemicellulase enzyme-G.
5. Gas flow which is in a liquid state (the composition of Methanol 2-Butoxyethanol Ethylene oxide nonylphenolpolymer Alcohols, C12-16, ethoxylated Tridecyl alcohol Nonylphenol Ethoxylated nonionic surfactant). It will flow back after fracturing.
6. Biocide is a composition formed from ingredients comprising peroxide and hypochlorite.
7. 20/40 size proppant.

### 2.2. Water Analysis

Generally, for every linear gel testing, we should check water quality because parameters of water will affect more during the formation of gel Hydration. If water has more pH, hardness, chlorides, iron leads to gel break very quickly. The following parameters should check before testing as shown in Table 1.

The water should be colourless, the turbidity of water should be low and the pH value should be 6-8. The chloride is determined by titration methods or chloride strips. The chlorides should be in the range up to <800 ppm. Iron can check by using the electronic instrument. Iron should be range up to <10 ppm.

Hardness was estimated by titration method and it should be in the range up to <100 ppm. Bicarbonate should be range <1000 ppm. Sulfates should be range <300 ppm. TDS should be range < 50,000 ppm. The reducing agent should be negative.



Fig. 3 Guar gum powder

Table 1: Test1 (sample water)

Parameters	Measured values
Clarity, colour, odour	Clear
Sample temperature, °C	26
Specific gravity	1
Initial pH	7.5
Iron (Fe <sup>2+</sup> /Fe <sup>3+</sup> ) ppm	1
Chloride, ppm	400
Total Hardness, ppm	80
Bicarbonate, ppm	800
Sulphates, ppm	200
TDS, ppm	30,000
Reducing Agent	Negative
Bacteria	500,000

Bacteria should be range <800,000. Specific Gravity of water can be determined by Hygrometer. Biocide was added to the water sample before testing to kill any bacteria.

### 2.3. Viscosity Measurement

A direct viscosity reading in centipoises (cp) was obtained by taking the 300 rpm reading of VG meter with Rheometer (FI spring, BI bob and Rotor). The viscosity of gel was measured when the gel exhibit stringy and pourable behaviour. So the apparent viscosity of gel was determined using the Fann 35 Rheometer.

### 3. Procedure for preparation of 1000 ml gel hydration

Take 309 ml of production water into Blender ought to look after velocity (1900-2000 rpm). Add 60 grams of Buffering agent like sodium hydroxide (or) sodium Bicarbonate (or) sodium acetate which should be in a powder state, mix until the material is dispersed and lump-free for 15 minutes. After mixing the buffering agent, the slurry should be maintained in basic nature [Fig. 4]. Need to check the basic nature by placing a pH strip into the slurry. Now add 240gm of guar gum and continue the mixing for 20 minutes (or) until the concentration of slurry is smooth and lump-free. Measure the density of the slurry. If the density of the slurry varies more than 0.1 ppg, refer to "cut

back (or) weight-up" charts to correct the slurry density. Measure the viscosity of the slurry, it should be maintained at 30-32 viscosity to pump the slurry.



Fig. 4 Instant linear gel

#### 4. Breaker Test

##### 4.1. Unit conversions

$$1\text{ppt} = \frac{1\text{pound}}{(1000 \times 1\text{gallon})} = \frac{1 \times 453.2}{(1000 \times 1 \times 3.782)} = \frac{453.2}{3782} = 0.12\text{gms / lit}$$

Where 453.2 grams is a factor, 1 gallon=3.782 lit


$$1\text{gpt} = \frac{1\text{gallon}}{1000\text{gallons}} = \frac{1\text{ltr}}{1000\text{ltr}} = \frac{1\text{ml}}{1000\text{ml}}$$

Now add 1ppt ammonium persulphate and 1gpt Enzyme-G into a linear Gel glass bottle and mix it well. Put it in water baths which are maintaining at 60°C and 45°C temperature, now check the viscosity for every 10 minutes.

##### 4.2. Fragmentation reaction

Initially, the gel viscosity is 30, under the gas well the bottom hole circulating temperature is 45°C and 60°C, by using 1ppt ammonium persulphate and 1gpt Enzyme-G breaker concentrations the fragmentation takes place, it means the gel viscosity will break gradually based on these temperatures and breaker concentration.

In order to break the gel viscosity very quickly, we can increase the breakers concentration.



In Table 2 we observed for every 10 minutes gel breaks gradually up to 180 minutes. Usually, the slurry pumping time is near to 30 minutes approximately. So in hydro frac operation, the gel carries 20-40 size sand, breaker's, and gas flow solution injected into well under high-pressure forms fissures.

**Table 2:** Test-2 Breaker Test Result (7.5 gpt gel under breaker concentration at 1ppt oxidizer and 1gpt Enzyme-G)

S. No	Gel Breaking Time (minutes)	Linear gel viscosity 1 ppt and 1 gpt breaker	
		60°C	45°C
1	0	30	30
2	10	27	28
3	20	25	26
4	30	23	24
5	40	20	21
6	50	17	19
7	60	15	17
8	90	11	14
9	120	8	10
10	150	5	7
11	180	0	2

After slurry pumped (i.e., after 30 minutes) the fragmentation reaction takes place, the breakers act on gel under bottom hole circulating temperature, 30 viscosity linear gel becomes watery gradually [Fig. 5]. After 180 minutes the gel totally will break and become water, the gas flow will return as flow backwater. This flow back water again we can use for production water after the reverse osmosis process.

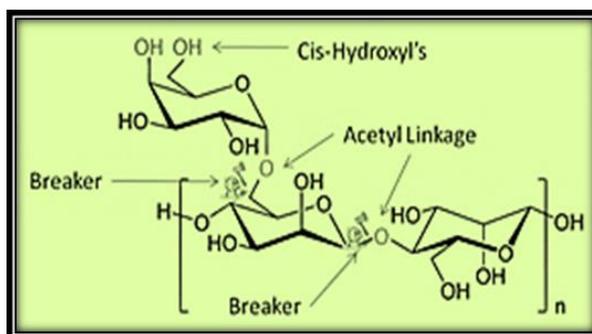


Fig. 5 Mechanism of Breaker test

## 5. Conclusion

The main focus of this research was to avoid the pollution in extreme operations, because of frac operation environment should be eco-friendly and naturally. The first objective of this research was the instead of hydrocarbons diesel, we used water for the preparation of linear gel. This is a direct mixing method; this linear gel effectively works in frac CBM onshore and offshore operations. Here less quantity of oxidizing agents (breakers) consumption take place. The main benefit is economically very less for frac operations. We conclude from the above experiment that without using any hazardous chemicals for preparation of linear gel observed good viscosity properties at bottom hole static temperature. This experiment is eco-friendly; the linear gel can also keep continuously in hydration tanks for 22 hours. So we can pump directly into well with high pressure and the used chemicals are very less hazardous. No smoke point for this linear gel because the gel prepared with water. So when compared with hydrocarbons diesel liner gel this water gel has many advantages in all aspects and worthless for extreme operations.

## Acknowledgement

The authors (s) wish to express their appreciation to BHI services frac Department, Essar oils for supporting their research project by providing the chemicals. We also express our Thanks to lab team members for assisting with this research.

## References

- [1] M.B. Smith & C. T. Montgomery (Eds.), In: Hydraulic Fracturing, 2<sup>nd</sup> ed., CRC Press, Boca Raton, 2015.
- [2] C. H. Yew & X. Weng, Mechanics of Hydraulic Fracturing, 2<sup>nd</sup> ed., Elsevier Inc., USA, 2015.
- [3] R.V.V.Ramana Murthy, M. Chavali, N.K. Kumer, Materials Today: Proceedings, 3,10 (2016), 3792.
- [4] Bikales Mark, Overberger, Georg Menges in Encyclopaedia of Polymer Science and Technology, Volume 7, 2<sup>nd</sup> Edition, John Wiley and Sons Inc., 1987, 587
- [5] W.Q. Peter R. Ellis., S.B.Ross-Murphy, Carbohyd. Polym, 64 (2006) 239.
- [6] E. A. R. and S. I. Kam, SPE Canadian Unconventional Resources Conference, Society of Petroleum Engineers, Calgary, CANADA, 2012.
- [7] R. S. Taylor, R. S. Lestz, Canadian International Petroleum Conference, Society of Canada, Calgary, CANADA 2006.
- [8] H.D. Brannon, D.E. Kendrick, E. Luckey, A. Stipetich, SPE Eastern Regional Meeting, Society of Petroleum Engineers, Charleston, West Virginia, USA, 2009.
- [9] W. Chen, O. Maurel, Journal of Petroleum Science and Engineering. 88 (2012) 67.
- [10] Leiming Li, Ghaithan A. Al-Muntasheri, Feng Liang, Petroleum, 2 (2016) 313.
- [11] Gupta, S. and P. S. Carman, Associative Polymer System Extends the Temperature Range of Surfactant Gel Frac Fluids, SPE International Symposium on Oilfield Chemistry, Society of Petroleum Engineers, (The Woodlands, Texas, USA, 2011)
- [12] Hyne, N. J., Nontechnical Guide to Petroleum Geology, Exploration, Drilling and Production, Pennwell Books, 2<sup>nd</sup> ed., USA, 2001.
- [13] Robert B Laughlin, Evaluation of Impacts to Underground Sources of Drinking Water by Hydraulic Fracturing of Coalbed Methane Reservoirs, Chapter 4, United States EPA, 2004 June, 1-26
- [14] James G. Speight, Handbook of Hydraulic Fracturing, John Wiley & Sons Inc., New Jersey, 2016
- [15] R.V.V.Ramana Murthy, N. K. Kumer, P.Satya Karuna and M.R.P.Reddy, Preparation of Cross Linker Liquid Frac Concentration (XLFC-1B) with different Hydrocarbons like Petrol, Diesel, Kerosene compatibility & Breaker Test by using oxidiser, breakers, J. Applicable. Chem. 2 (2013) 605.
- [16] A.V.L.N.S.H. Hariharan, D.Murali Krishna, J.Applicable.Chem. 1 (2012) 39.
- [17] M. Umayavalli, N. Krishnaveni and G.Siva Kumar, J. Applicable. Chem. 2 (2013) 1701.
- [18] Jyoti kundal, Reena Purohit, Rajendra Singh and M.C Purohit, Antimicrobial and Antioxidant Activities of Bark Extract of *Myrica Esculenta*, J.Applicable.Chem. . 2 (2013) 1141.
- [19] Georgi E. Chernev, Lyudmila V. Kabaivanova, Isabel M.Miranda Salvado, Elena V. Todorova and Juliana G. Ivanova, Sol-Gel Hybrid Materials Applied As Matrices For A Co-Immobilized System of Bacteria and Algae. J. Applicable. Chem. 2 (2013) 1665.
- [20] A.Rajendiran, K. Krishnasamy, S.Kabilan, G.Vasudev and S.Kumar, J. Applicable. Chem. 2 (2013) 264.
- [21] K.S. Sorbie (1991) Polymer Improved Oil Recovery. Springer Science, New York, USA